

TSC Series

Applications

Viewing windows, wet bench tanks and semiconductor applications

Characteristics

Flame fused quartz block and hollow material with low bubble content

TSC-3® fused quartz is produced in a flame fusion process from refined natural quartz powder. The production process ensures a low alkali content. The long furnace residence time guarantees a low bubble content, resulting in excellent visual properties.

TSC-4 additionally offers a reduced aluminium content.

TSC-Synthetic has very high purity and is produced from synthetic fused silica powder. It has excellent visual quality with no bubbles larger than 0.1 mm. The high purity of TSC-Synthetic ensures excellent deep UV transmission. TSC-Synthetic is available in large sizes (up to 600 mm x 2000 mm).



Heraeus transparent ingots are available in rectangular, round and hollow shapes and a wide range of sizes. Ingots can be cut and ground or lapped to make blanks in a variety of shapes including rectangular or square plates, disks and rings.

Available Dimensions

Rectangular Ingots (Length up to 2200 mm)

Thickness	200 mm			
	160 mm			
	120 mm			
Width	< 450 mm	< 540 mm	< 670 mm	

Hollow Ingots

	mm
OD	Up to 670
OD tolerance	+4 / -0
Wall Thickness	>= 15

Round Ingots

Length	2300 mm				
	1900 mm				
	210 mm				
	160 mm				
	120 mm				
Diameter	< 310 mm	< 350 mm	< 420 mm	< 540 mm	< 670 mm

Chemical Purity – Typical trace elements and OH content in quartz glass (ppm by weight oxide)


Elements	Al	Ca	Cr	Cu	Fe	K	Li	Mn	Na	Nd	Ti	Y	Zr	OH
TSC-3®	15	0.5	<0.01	<0.01	0.1	0.2	0.2	0.01	0.1	0.1	1.3	<0.1	1.3	170
TSC-4	8	0.4	<0.01	<0.01	0.2	0.05	0.2	<0.01	<0.08	<0.1	1.5	<0.01	0.5	170
TSC-Synthetic	<0.04	<0.01	<0.01	<0.01	<0.01	<0.01	<0.01	0.01	<0.01	0.15	0.01	0.01	0.02	130

Technical properties

	TSC-3®	TSC-4	TSC-Synthetic
Mechanical Data			
Density (g/cm ³)	2,2	2,2	2,2
Mohs Hardness	5,5 ... 6,5	5,5 ... 6,5	5,5 ... 6,5
Micro Hardness (N/mm ²)	8600 ... 9800	8600 ... 9800	8600 ... 9800
Knoop Hardness (N/mm ²)	5800 ... 6100	5800 ... 6100	5800 ... 6100
Modulus of elasticity at 20°C (N/mm ²)	7.3 x 10 ⁴	7.3 x 10 ⁴	7.3 x 10 ⁴
Modulus of torsion (N/mm ²)	3.0 x 10 ⁴	3.0 x 10 ⁴	3.0 x 10 ⁴
Poisson's ratio	0.16	0.16	0.16
Compressive strength (approx.) (N/mm ²)	1110	1110	1110
Tensile strength (approx.) (N/mm ²)	50	50	50
Bending strength (approx.) (N/mm ²)	65	65	65
Torsional strength (approx.) (N/mm ²)	30	30	30
Sound velocity (m/s)	5700	5700	5700
Thermal Data			
Softening temperature (°C)	1730	1730	1730
Annealing temperature (°C)	1200	1200	1200
Strain temperature (°C)	1080	1080	1080
Max. working temperature continuous (°C)	1050	1050	1050
short-term (°C)	1350	1350	1350

Typical Transmission Spectrum (including Fresnel reflection losses)

Sample thickness: 10mm

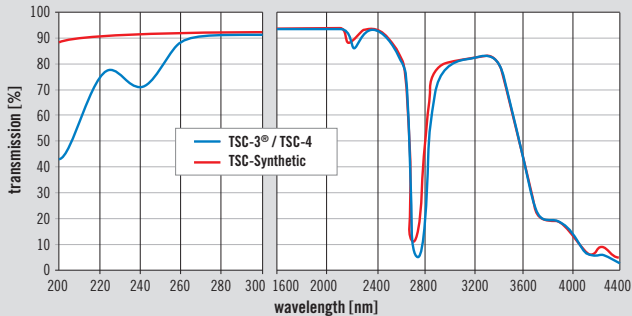

Europe
Heraeus Quarzglas GmbH & Co. KG
 Base Materials
 Reinhard-Heraeus-Ring 29,
 63801 Kleinostheim
 Germany
 Phone: +49 (6181) 35-7444
 Fax +49 (6181) 35-7210
 sales.hqs.basematerials.de
 @heraeus.com

Europe
Heraeus Quartz UK Ltd.
 Neptune Road
 Wallsend
 Tyne & Wear
 NE28 6DD
 United Kingdom
 Phone +44 (191) 262 5311
 Fax +44 (191) 263 8040
 sales.hqs.tsc.uk
 @heraeus.com

Asia
Heraeus ShinEtsu Quartz (China) Inc.
 QianJiang Tower
 20th Floor, Room A
 No. 971 Dongfang Road
 200122 Shanghai, China
 Phone +86 (21) 68672266-809
 Fax +86 (21) 68751434
 sales.hqs.basematerials.cn
 @heraeus.com

North America
Heraeus Quartz America LLC
 Base Materials Division
 2400 Grand Avenue Parkway
 Suite 102
 Austin, TX 78728
 USA
 Phone: (+1) 512 989 05 03
 Fax: (+1) 512 989 05 04
 sales.hqs.basematerials.us
 @heraeus.com

www.base-materials.heraeus-quarzglas.com

	TSC-3®	TSC-4	TSC-Synthetic
Mean specific heat (J/kg*K)			
0 ... 100°C	772	772	772
0 ... 500°C	964	964	964
0 ... 900°C	1052	1052	1052
Heat conductivity (W/m*K)			
20°C	1.38	1.38	1.38
100°C	1.47	1.47	1.47
200°C	1.55	1.55	1.55
300°C	1.67	1.67	1.67
400°C	1.84	1.84	1.84
950°C	2.68	2.68	2.68
Mean expansion coefficient (K⁻¹)			
0 ... 100°C	5.1 x 10 ⁻⁷	5.1 x 10 ⁻⁷	5.1 x 10 ⁻⁷
0 ... 200°C	5.8 x 10 ⁻⁷	5.8 x 10 ⁻⁷	5.8 x 10 ⁻⁷
0 ... 300°C	5.9 x 10 ⁻⁷	5.9 x 10 ⁻⁷	5.9 x 10 ⁻⁷
0 ... 600°C	5.4 x 10 ⁻⁷	5.4 x 10 ⁻⁷	5.4 x 10 ⁻⁷
0 ... 900°C	4.8 x 10 ⁻⁷	4.8 x 10 ⁻⁷	4.8 x 10 ⁻⁷
-50 ... 0°C	2.7 x 10 ⁻⁷	2.7 x 10 ⁻⁷	2.7 x 10 ⁻⁷

Electric Data

	TSC-3®	TSC-4	TSC-Synthetic
Electrical resistivity in Ω x m			
20°C	10 ¹⁶	10 ¹⁶	10 ¹⁶
400°C	10 ¹⁰	10 ¹⁰	10 ¹⁰
800°C	6.3 x 10 ⁶	6.3 x 10 ⁶	6.3 x 10 ⁶
1200°C	51.3 x 10 ⁵	51.3 x 10 ⁵	51.3 x 10 ⁵
Dielectric strength in KV/mm (sample thickness ≥ 5 mm)			
20°C	25 ... 40	25 ... 40	25 ... 40
500°C	4 ... 5	4 ... 5	4 ... 5
Dielectric loss angle (tg δ)			
1kHz	5.0 x 10 ⁻⁴	5.0 x 10 ⁻⁴	5.0 x 10 ⁻⁴
1MHz	1.0 x 10 ⁻⁴	1.0 x 10 ⁻⁴	1.0 x 10 ⁻⁴
3 x 10 ¹⁴ Hz	4.0 x 10 ⁻⁴	4.0 x 10 ⁻⁴	4.0 x 10 ⁻⁴
Dielectric constant (ε)			
20°C 0 ... 10 ⁶ Hz	3.70	3.70	3.70
23°C 9 ... 10 ⁸ Hz	3.77	3.77	3.77
23°C 3 ... 10 ¹⁰ Hz	3.81	3.81	3.81

www.base-materials.heraeus-quarzglas.com